

11-53401
(ACCESSION NUMBER)
12
(PAGES)
TMX-59483
(NASA CR OR TMX OR AD NUMBER)

(THRU)
(COPIES)
(CATEGORY)

Facility
INPUT

AD

RSIC-640

**EFFECT OF CERTAIN ADDITIVES ON THE THERMAL
DECOMPOSITION OF AMMONIUM PERCHLORATE**

by

A. A. Shidlovskiy
L. F. Shmagin
V. V. Bulanova

Izvestiya Vysshikh Uchebnykh Zavedeniy SSSR
"Khimiya i Khimicheskaya Tekhnologiya" No. 4, 533-538 (1965)

Translated from the Russian

January 1967

DISTRIBUTION OF THIS DOCUMENT IS UNLIMITED

REDSTONE SCIENTIFIC INFORMATION CENTER
REDSTONE ARSENAL, ALABAMA

JOINTLY SUPPORTED BY



U.S. ARMY MISSILE COMMAND



GEORGE C. MARSHALL SPACE FLIGHT CENTER

Disclaimer

The findings of this report are not to be construed as an official Department of the Army position.

Disposition

Destroy this report when it is no longer needed. Do not return it to the originator.

167

25 January 1967

RSIC-640

**EFFECT OF CERTAIN ADDITIVES ON THE THERMAL
DECOMPOSITION OF AMMONIUM PERCHLORATE**

by

A. A. Shidlovskiy
I. F. Shmagin
V. V. Bulanova

Izvestiya Vysshikh Uchebnykh Zavedeniy SSSR
"Khimiya i Khimicheskaya Tekhnologiya" No. 4, 533-538 (1965)

Translated from the Russian

DISTRIBUTION OF THIS DOCUMENT IS UNLIMITED

Translation Branch
Redstone Scientific Information Center
Research and Development Directorate
U. S. Army Missile Command
Redstone Arsenal, Alabama 35809

The thermal decomposition of perchlorate of ammonium (PA), pure as well as with additives, is dealt with in many papers. The kinetics of the decomposition have been studied essentially by measuring the pressure or volume of the evolving gases.

Bircumshaw and Newman¹ investigated the decomposition of PA at 215° to 275°C. They found that the decomposition of PA starts on the surface and propagates in the form of half-spheres which later combine into a continuous front. The process ceases after the decomposition of about 30 percent of the salt. The residue represents a friable powder which is identical with the original PA. The energy of activation of the decomposition of PA is $E = 27.8$ kcal/mole (1 kcal = 4.1868 joules) for the orthorhombic and $E = 18.9$ kcal/mole for the cubic form.

Galwey and Jacobs² investigated the decomposition of PA by the manometric method and found $E = 24.6$ kcal/mole for the orthorhombic and cubic forms of the PA. They confirmed the indication¹ that at a temperature above 300°C the PA decomposes completely. Galwey and Jacobs³ found $E = 17.5$ kcal/mole for the decomposition of PA and $E = 30$ kcal/mole for the decomposition of the residue from the low-temperature reaction at a temperature above 350°C. While measuring the delay in the ignition as a function of the temperature, they found $E = 41.1$ kcal/mole⁴.

Rayevskiy and Manelis⁵, while measuring by the method of microphotography the rate of growth of the nuclei of the decomposition of the PA, found $E = 31$ to 33 kcal/mole. Sun Tsuan-tsai⁶ studied, by the manometric method, the decomposition of PA and found by different methods of calculation that the energy of activation was about 30 kcal/mole. According to data by Osada and Sakamoto⁷, the energy of activation of the decomposition of PA depends on the size of the particles. The energy of activation of the decomposition of PA with additives of metal oxides is, according to literature data, about 30 kcal/mole and depends little on the chemical nature of the oxide. A study was made of the decomposition of PA with additives of the oxides MnO_2 ^{8,9,10}, Cu_2O ^{11,12,10}, CuO ^{13,10}, ZnO ^{14,10}, Fe_2O_3 ¹⁵, MgO ^{16,9}, Cr_2O_3 ^{9,10}, Ni_2O_3 , $\text{Co}_2\text{O}_3 + \text{Co}_3\text{O}_4$ ⁹, as well as the chlorides of metals⁷. The action of the catalytic additives is explained by their participation in the process of electron transfer from ClO_4^- to NH_4^+ .

The purpose of this work was to study the thermal decomposition of PA, pure and in the presence of oxides, chlorides, carbonates, and oxalates of certain metals.

EXPERIMENTAL SECTION


The study of the kinetics of thermal decomposition was conducted by the gravimetric method. The decomposition was conducted in an air atmosphere at atmospheric pressure. The free removal of the decomposition products excluded their influence on the decomposition of PA⁶. The substance (about 150 mg) was placed in a glass cup which was, by means of a glass capillary, lowered into an oven previously heated to the given temperature and suspended on a lever of a torsion balance VT-200 (accuracy of weighing 0.2 mg). The temperature in the oven was controlled with an accuracy of $\pm 1^\circ\text{C}$.

The PA, recrystallized from water, was dried at 100° to 110°C , ground, and sifted through a 018 sieve. In all the experiments, use was made of one specimen of PA which was stored in a desiccator over anhydrous calcium chloride.

The kinetics of decomposition of pure PA were studied within the temperature limits of 214° to 470°C . Figure 1 shows the decomposition curves $\alpha - t$ (degree of decomposition--time) of pure PA and the decomposition curve at 410°C of the residue from the low-temperature reaction (at 230°C). Decomposition of the orthorhombic form of PA ($t < 240^\circ\text{C}$) is characterized by the existence of an induction period, period of acceleration, and period of drop in the speed of decomposition which corresponds to the formation, growth, and intergrowth of the centers of decomposition into a continuous front¹. The decomposition stops upon the achievement of $\alpha = 30$ percent, after which, a white, porous, slightly sintered residue of PA remains. The maximum rate of decomposition develops for α of about 10 percent.

The decomposition of the cubic form of PA (240° to 300°C) proceeds without an induction period. The rate of decomposition reaches a maximum for $\alpha = 3$ to 5 percent. On the decomposition curve, one can distinguish three periods: period of acceleration, period of rapid decomposition, and period with a considerably smaller, almost constant rate. The changeover to gradual decomposition takes place for $\alpha = 20$ to 30 percent; besides, the higher the temperature of decomposition, the greater the α at which this changeover takes place.

At 300° to 380°C , the reproducibility of the kinetic curves is poor as a result of a change in the mechanism of the decomposition of the PA³. At a temperature above 380°C , the rate of decomposition of PA decreases with time. The decomposition is complete.

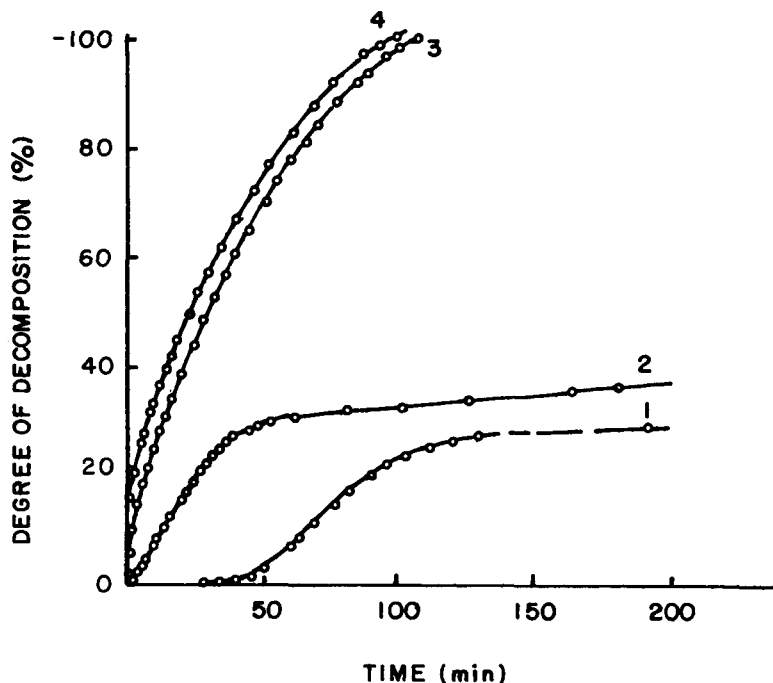

1-230°C, 2-281°C, 3-410°C, and 4-410°C
(residue from low-temperature reaction).

Figure 1. Decomposition Curves of Ammonium Perchlorate

A study was made of the decomposition of the residue from the low-temperature reaction (at 230°C). For this purpose, the residue, after the reaction had ceased, was transferred to another oven and its decomposition was studied. The decomposition curves of the residue are reproducible at temperatures above 380°C. Decomposition was complete. The maximum rate of decomposition of the residue was greater for the original PA. The residue from the low-temperature reaction burns up 1 to 2 minutes after immersion of the specimen in the oven which had been heated to 450°C, whereas the original PA catches fire at 470°C. At a temperature above 300°C, a noticeable sublimation of the PA was observed.

A kinetic analysis of the decomposition curves was conducted with the help of the Yerofeyev equation¹⁷,

$$-\ln(1 - a) = kt^n, \quad (1)$$

where a is the degree of decomposition at the time t , and k is a constant. The values of k and n were determined from the curves of $\lg[-\lg(1 - a)] - \lg t$. The values of the constant, k , obtained from these curves, were recalculated in accordance with the Sakovich equation¹⁷,

$$K = nk \cdot t^n, \quad (2)$$

where K is a rate constant with the dimension of the rate constant of the monomolecular reaction (t^{-1}), and k is the constant from the Yerofeyev equation.


The limits of applicability of the Yerofeyev equation are listed in Table I. The straight lines, $\lg[-\lg(1 - \alpha)] - \lg t$, corresponding to the decomposition of the PA and the residue from the low-temperature reaction, at a temperature above 380°C have breaks at $\alpha = 40$ to 50 per cent. At the same time, different values of n and k are obtained for the start and end of the decomposition.

Table I. Kinetic Characteristics of the Thermal Decomposition of Ammonium Perchlorate

Decomposition Temperature, $^\circ\text{C}$	Limits of Applicability of the Yerofeyev Equation of α , %	Index of Degree, n	Preexponential Multiplier, C	Energy of Activation, E (kcal/mole)
214 to 236	0 to 12	4.5	$1.6 \cdot 10^{16}$	40.1
250 to 300	0 to 20	1.2	$1.3 \cdot 10^8$	25.1
400 to 470	10 to 50	0.8	$2.0 \cdot 10^7$	28.3
400 to 470	50 to 90	1.1	$1.1 \cdot 10^6$	23.7
330 to 450*	0 to 40	0.6	$4.5 \cdot 10^{10}$	39.1
330 to 450*	40 to 80	1.0	$5.9 \cdot 10^9$	35.5

*Residue from low-temperature reaction.

The magnitudes of the energy of activation were determined from the curves of $\lg K = 1/T$ (Figure 2). It is seen in Figure 2 that the phase transition at 240°C and the change in the decomposition mechanism at 300° to 380°C ³ cause a sharp drop in the rate constant. There is just as sharp a change at these temperatures in the value of the maximum rate of decomposition of PA. The resulting value of $n = 4.5$ for the orthorhombic form corresponds to the value by Galwey and Jacobs⁴. During decomposition of the cubic form of PA, the index of the degree is close to unity and even less than it; i. e., the reaction becomes monomolecular and changes into the diffusion realm¹⁷.

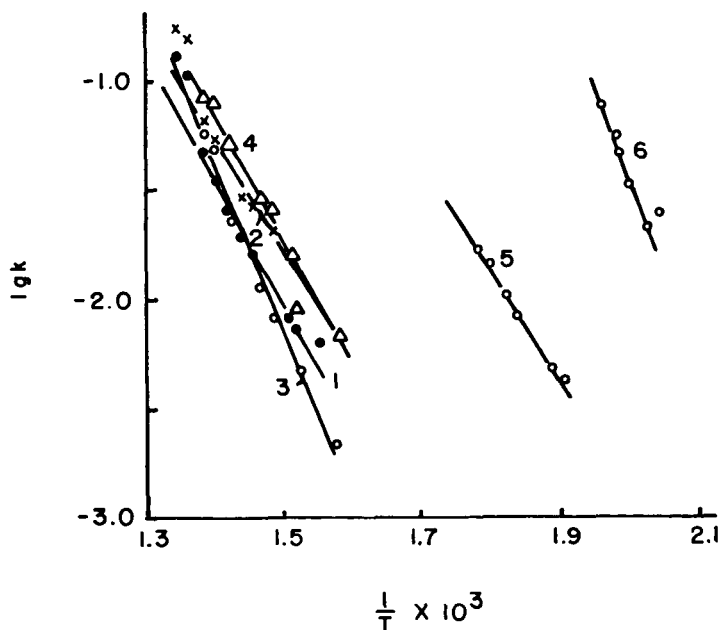

1- $t > 380^{\circ}\text{C}$, $\alpha < 50$ Percent; 2- $t > 380^{\circ}\text{C}$, $\alpha > 50$ Percent; 3-Residue from Low-Temperature Reaction $t > 380^{\circ}\text{C}$, $\alpha < 40$ Percent; 4-Residue from Low-Temperature Reaction, $t > 380^{\circ}\text{C}$, $\alpha = 40 - 80$ Percent; 5- $t = 240^{\circ} - 300^{\circ}\text{C}$; 6- $t = 214^{\circ} - 236^{\circ}\text{C}$.

Figure 4. Dependence of $\lg K$ on $1/T$ During Decomposition of Ammonium Perchlorate

The value of the energy of activation which we obtained for the orthorhombic form of PA was somewhat higher than in other words^{1, 2, 3} this can be explained by the fact that, during decomposition of PA in a closed space, side reactions can take place which influence the decomposition. In our experiments, the removal of the decomposition products was free. The value of the energy of activation for the decomposition of the residue from the low-temperature reaction is at $t > 380^{\circ}\text{C}$ close to E obtained during⁴ a study of the delay time of ignition. The decomposition of the original PA at this temperature proceeds with a considerably smaller E , which is possibly connected with the influence of the intercrystallite material.

THERMAL DECOMPOSITION OF PA WITH ADDITIVES

As additives in the thermal decomposition of PA, use was made essentially of compounds (oxides, chlorides, carbonates, and oxalates) of d-elements of the IV period of the Mendeleyev periodic system (from V to

Zn) in the form of standard ("analytical grades" or "pure" grades) or of preparations synthesized by us^{18,19,20}. The additives were ground and sifted through a 018 sieve. The additive content was most frequently 5 percent by weight: such a large amount of additive was taken in order to determine clearly the nature of its influence. The mixtures were prepared by mechanical mixing of the additive samples and of the PA (the same specimen of PA was used as during the decomposition of the pure PA). The ready mixtures were stored in a desiccator over anhydrous calcium chloride.


Table II lists the data on the influence of metal oxides on the thermal decomposition of the PA.

Table II. Kinetic Characteristic of the Thermal Decomposition of Ammonium Perchlorate in the Presence of Metal Oxides

Additive (5%)	Temperature Limits, *°C	Index of Degree, n	Energy of Activation, E (kcal/mole)	Preexponential Multiplier, C
MnO ₂ (According to Frem ¹⁸)	208 to 229	1.6	48.2	$2.4 \cdot 10^{17}$
MnO ₂ (pyrolusite)	214 to 245	1.4	33.7	$5.0 \cdot 10^{12}$
Co ₂ O ₃	214 to 245	1.4	38.3	$7.4 \cdot 10^{14}$
CuO	239 to 270	2.2	53.5	$5.0 \cdot 10^{20}$
Cu ₂ O	250 to 270	1.6	45.5	$1.4 \cdot 10^{17}$
Fe ₂ O ₃	250 to 296	1.2	41.0	$2.6 \cdot 10^{14}$
NiO	270 to 296	1.2	49.2	$6.3 \cdot 10^{17}$
V ₂ O ₅	250 to 303	1.2	43.7	$1.6 \cdot 10^{15}$
Cr ₂ O ₃	260 to 309	1.1	30.1	$8.0 \cdot 10^9$

*At a temperature above the upper limit, the mixtures burst into flame.

It is seen from Table II that the action of the additive depends on the chemical nature of the oxide. Figure 3 shows the decomposition curves of PA in the presence of some oxides.

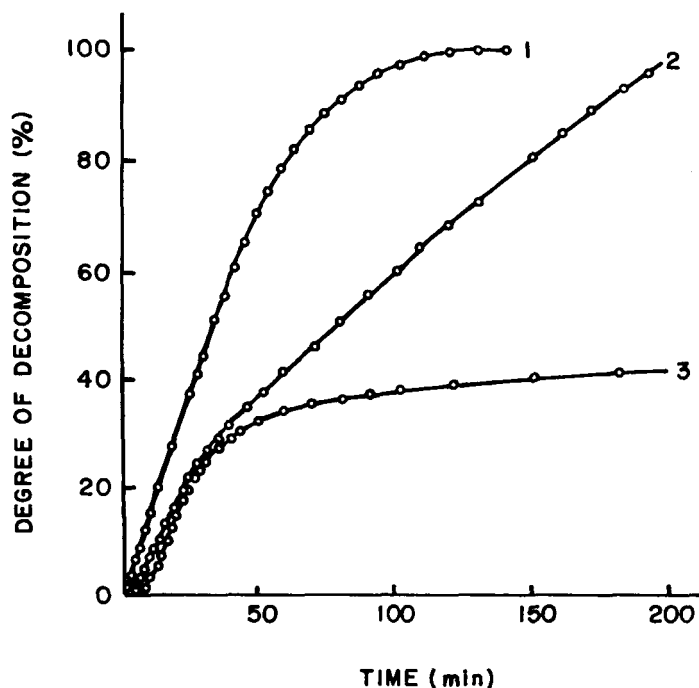

1-MnO₂ (according to Frem), 224°C; 2-NiO, 280°C; 3-CuO, 260°C

Figure 3. Decompositon Curves of Ammonium Perchlorate in the Presence of 5 Percent by Weight of Oxides

The strongest influence on the thermal decomposition of PA is exerted by the compounds of manganese (MnO₂, MnCO₃, MnCl₂·4H₂O) and cobalt (Co₂O₃, CoCO₃, CoC₂O₄, CoCl₂·6H₂O). In the presence of these additives, the PA decomposes completely even at 210° to 220°C. The induction period is in most cases, absent. The rate of decomposition of PA changes practically in proportion to the content of the additive within the limits of 1 to 5 percent.

In the presence of copper compounds (Figure 3), the maximum decomposition rate increases. The degree of decomposition increases insignificantly (Figure 3). The decomposition curves of PA in the presence of copper compounds do not change their nature (the induction period at a temperature lower than 240°C is shortened.) Mixtures of PA with 5 percent CuCO₃, Cu₂O, CuO, and Cu₂Cl₂·2H₂O burn at temperatures of 265°, 275°, 280°, 285°, and 287°C, respectively. After the mixtures burned, a greenish scale remained on the cup; this was soluble in water, with the formation of a bluish solution, i. e., CuCl₂ formed. By changing the content of copper compounds within the limits of 1 to 5 percent, their influence on the decomposition of PA does not change.

Compounds of iron (Fe_2O_3 , FeC_2O_4 , $\text{FeCl}_3 \cdot 6\text{H}_2\text{O}$), nickel (NiO , NiC_2O_4 , $\text{NiCO}_3 \cdot \text{Ni}(\text{OH})_2$, $\text{NiCl}_2 \cdot 6\text{H}_2\text{O}$), chromium (Cr_2O_3 , $\text{CrCl}_3 \cdot 6\text{H}_2\text{O}$), and vanadium (V_2O_5) influence the decomposition of PA at a temperature above 240°C .

At the same time, the maximum rate of decomposition of PA decreases, while the rate of decomposition in the third, the slowest, period increases (Figure 3). At 270° to 280°C , PA with these additives decomposes completely. Within limits of 1 to 5 percent, the rate of decomposition in the third period is proportional to the additive. The maximum rate decreases with a decrease to a certain limit in the amount of these additives. This limit amounts to about 2.5 percent for compounds of iron and nickel (II), and less than 1 percent for compounds of chromium and vanadium. With a further decrease in the amount of the additive, the maximum rate increases and approaches the maximum rate of decomposition of the pure PA. The oxides, MgO and ZnO , upon being heated, enter into chemical reaction with the PA. At the same time, a liquid phase results, which, apparently, serves to explain the influence of these additives on the decomposition of the PA.

It should be pointed out that the introduction of most tested additives strongly reduces the ignition point of the PA.

Table III lists data on the thermal decomposition of PA in the presence of different compounds of cobalt.

Table III. Kinetic Characteristics of the Decomposition of Ammonium Perchlorate in the Presence of Cobalt Compounds

Additive (5%)	Temperature Limits*, $^\circ\text{C}$	Index of Degree, n	Energy of Activation, E (kcal/mole)	Preexponential Multiplier, C
CoCO_3	208 to 224	1.4	46.7	$1.4 \cdot 10^{19}$
CoC_2O_4	210 to 229	1.7	43.7	$5.4 \cdot 10^{17}$
Co_2O_3	214 to 245	1.4	38.3	$7.4 \cdot 10^{14}$
$\text{CoCl}_2 \cdot 6\text{H}_2\text{O}$	214 to 250	1.1	36.0	$6.3 \cdot 10^{13}$

*At a temperature above the upper limit, the mixtures caught fire in the oven.

It is seen from Table III that the action of the additives depends on the nature of the chemical compound of the given element. The activity of the additive decreases in the following order: carbonates (oxalates), oxides, and chlorides. During the thermal decomposition of the PA, all the additives which we tested changed into oxides that are most characteristic for the given metal. The activity of the additive is apparently determined by the ease of its conversion into the oxide and the properties of the resulting oxide.

CONCLUSIONS

1) A study was made of the thermal decomposition of PA at 214° to 470°C by the gravimetric method in an air atmosphere. The following values of the energies of activation of the decomposition have been determined: orthorhombic form, $E = 40$ kcal/mole; cubic form, $E = 24$ to 28 kcal/mole; and residue from low-temperature reaction, $E = 36$ to 39 kcal/mole.

2) A study was made of the influence of oxides, chlorides, carbonates, and oxalates of a number of metals on the thermal decomposition of PA. It was shown that the compounds of manganese and cobalt lead to complete decomposition of the PA at a temperature below 240°C. The compounds of iron, nickel, and chromium lead to complete decomposition of PA at 270° to 280°C.

3) At the same temperature, the maximum rate of decomposition of PA with additives of the compounds of Cu, Mn, Co, as well as ZnO is greater than the maximum decomposition rate of the pure PA; the maximum decomposition rate of mixtures of PA with compounds of iron, nickel (II), chromium, as well as V_2O_5 is less than for pure PA.

4) The activity of additives of the same element decreases in the following order: carbonate (oxalate), oxide, and chloride.

LITERATURE CITED

1. L. L. Bircumshaw and B. H. Newman, Proceedings of the Royal Society, Vol. A227, No. 1168, 1954, p. 115; No. 1169, 1955, p. 228.
2. A. K. Galwey and P. W. M. Jacobs, Proceedings of the Royal Society, Vol. A254, 1960, p. 455.
3. A. K. Galwey and P. W. M. Jacobs, Journal of the Chemical Society, 1959, p. 837.
4. A. K. Galwey and P. W. M. Jacobs, Journal of the Chemical Society, 1960, p. 5031.
5. A. V. Rayevskiy and G. B. Manelis, Dokl. AN SSSR, (Reports of Acad. Sci. USSR), 1963, p. 886.
6. Sun Tsuan-tsai, Candidate Dissertation (Moscow, 1961).
7. H. Osada and E. Sakamoto, J. Ind. Expl. Soc., Japan, Vol. 24, 1963, p. 236.
8. A. K. Galwey and P. W. M. Jacobs, Trans. Faraday. Soc., Vol. 55, 1959, p. 1165.
9. A. Hermoni and A. Salmon, Eighth Symposium (International) on Combustion, Pasadena, 1960, p. 656.
10. K. Kuratani, Tokyo Daigaku Konu Kenkyusho Hokoku, Vol. 88, 1961, p. 79; Chemical Abstract, Vol. 59, 1963, p. 4965.
11. P. W. M. Jacobs and A. R. T. Kureishy, Journal of the Chemical Society, 1962, p. 556.
12. P. W. M. Jacobs and A. R. T. Kureishy, Eighth Symposium (International) on Combustion, Pasadena, 1960, p. 672.
13. F. Solymosi, E. Krix, and J. Catalysis, Vol. 1, 1962, p. 468.
14. F. Solymosi and L. Révész, Nature, Vol. 192, 1961, p. 64.
15. F. Solymosi and L. Révész, Kinetika i Kataliz (Kinetics and Catalysis), Vol. 4, 1963, p. 88.
16. A. Hermoni (Makovky) and A. Salmon, Bull. Res. Council, Israel, Vol. A9, 1960, p. 206.
17. V. V. Boldyrev. METODY IZUCHENIYA KINETIKI TERMICHESKOGO RAZLOZHENIYA TVERDYKH VESHCHESTV (METHODS OF STUDYING THE DECOMPOSITION OF SOLID SUBSTANCES), Publishing House of Tomsk University, Tomsk, 1958.

18. Ye. V. Alekseyevskiy, AKTIVNAYA DUVOKIS' MARGANTSA (ACTIVE MANGANESE DIOXIDE), ONTI, Leningrad, 1937.
19. Yu. V. Karyakin and I. I. Angelov, CHISTYYE KHIMICHESKIYE REAKTIVY (PURE CHEMICAL REAGENTS), Goskhimizdat, Moscow, 1955.
20. G. Brauer, RUKOVODSTVO PO PREPARATIVNOY NEORGANICHESKOY KHIMII (TEXTBOOK ON PREPARATIVE INORGANIC CHEMISTRY), Foreign Language Publishing House, 1956.

DISTRIBUTION

	No. of Copies		No. of Copies
<u>EXTERNAL</u>		U. S. Atomic Energy Commission	1
Air University Library	1	ATTN: Reports Library, Room G-017	
ATTN: AUL3T		Washington, D. C. 20545	
Maxwell Air Force Base, Alabama 36112		U. S. Naval Research Laboratory	1
U. S. Army Electronics Proving Ground	1	ATTN: Code 2027	
ATTN: Technical Library		Washington, D. C. 20390	
Fort Huachuca, Arizona 85613		Weapons Systems Evaluation Group	1
U. S. Naval Ordnance Test Station	1	Washington, D. C. 20305	
ATTN: Technical Library, Code 753		John F. Kennedy Space Center, NASA	2
China Lake, California 93555		ATTN: KSC Library, Documents Section	
U. S. Naval Ordnance Laboratory	1	Kennedy Space Center, Florida 32899	
ATTN: Library		APGC (PGBPS-12)	1
Corona, California 91720		Eglin Air Force Base, Florida 32542	
Lawrence Radiation Laboratory	1	U. S. Army CDC Infantry Agency	1
ATTN: Technical Information Division		Fort Benning, Georgia 31905	
P. O. Box 808		Argonne National Laboratory	1
Livermore, California 94550		ATTN: Report Section	
Sandia Corporation	1	9700 South Cass Avenue	
ATTN: Technical Library		Argonne, Illinois 60440	
P. O. Box 969		U. S. Army Weapons Command	1
Livermore, California 94551		ATTN: AMSWE-RDR	
U. S. Naval Postgraduate School	1	Rock Island, Illinois 61201	
ATTN: Library		Rock Island Arsenal	1
Monterey, California 93940		ATTN: SWERI-RDI	
Electronic Warfare Laboratory, USAECOM	1	Rock Island, Illinois 61201	
Post Office Box 205		U. S. Army Cmd. & General Staff College	1
Mountain View, California 94042		ATTN: Acquisitions, Library Division	
Jet Propulsion Laboratory	2	Fort Leavenworth, Kansas 66027	
ATTN: Library (TDS)		Combined Arms Group, USACDC	1
4800 Oak Grove Drive		ATTN: Op. Res., P and P Div.	
Pasadena, California 91103		Fort Leavenworth, Kansas 66027	
U. S. Naval Missile Center	1	U. S. Army CDC Armor Agency	1
ATTN: Technical Library, Code N3022		Fort Knox, Kentucky 40121	
Point Mugu, California 93041		Michoud Assembly Facility, NASA	1
U. S. Army Air Defense Command	1	ATTN: Library, I-MICH-QSD	
ATTN: ADSX		P. O. Box 29300	
Ent Air Force Base, Colorado 80912		New Orleans, Louisiana 70129	
Central Intelligence Agency	4	Aberdeen Proving Ground	1
ATTN: OCR/DD-Standard Distribution		ATTN: Technical Library, Bldg. 313	
Washington, D. C. 20505		Aberdeen Proving Ground, Maryland 21005	
Harry Diamond Laboratories	1	NASA Sci. & Tech. Information Facility	5
ATTN: Library		ATTN: Acquisitions Branch (S-AK/DL)	
Washington, D. C. 20438		P. O. Box 33	
Scientific & Tech. Information Div., NASA	1	College Park, Maryland 20740	
ATTN: ATS		U. S. Army Edgewood Arsenal	1
Washington, D. C. 20546		ATTN: Librarian, Tech. Info. Div.	
		Edgewood Arsenal, Maryland 21010	

	No. of Copies		No. of Copies
National Security Agency ATTN: C3/TDL Fort Meade, Maryland 20755	1	Brookhaven National Laboratory Technical Information Division ATTN: Classified Documents Group Upton, Long Island, New York 11973	1
Goddard Space Flight Center, NASA ATTN: Library, Documents Section Greenbelt, Maryland 20771	1	Watervliet Arsenal ATTN: SWEVW-RD Watervliet, New York 12189	1
U. S. Naval Propellant Plant ATTN: Technical Library Indian Head, Maryland 20640	1	U. S. Army Research Office (ARO-D) ATTN: CRD-AA-IP Box CM, Duke Station Durham, North Carolina 27706	1
U. S. Naval Ordnance Laboratory ATTN: Librarian, Eva Liberman Silver Spring, Maryland 20910	1	Lewis Research Center, NASA ATTN: Library 21000 Brookpark Road Cleveland, Ohio 44135	1
Air Force Cambridge Research Labs. L. G. Hanscom Field ATTN: CRMCLR/Stop 29 Bedford, Massachusetts 01730	1	Systems Engineering Group (RTD) ATTN: SEPIR Wright-Patterson Air Force Base, Ohio 45433	1
Springfield Armory ATTN: SWESP-RE Springfield, Massachusetts 01101	1	U. S. Army Artillery & Missile School ATTN: Guided Missile Department Fort Sill, Oklahoma 73503	1
U. S. Army Materials Research Agency ATTN: AMXMR-ATL Watertown, Massachusetts 02172	1	U. S. Army CDC Artillery Agency ATTN: Library Fort Sill, Oklahoma 73504	1
Strategic Air Command (OAI) Offutt Air Force Base, Nebraska 68113	1	U. S. Army War College ATTN: Library Carlisle Barracks, Pennsylvania 17013	1
Picatinny Arsenal, USAMUCOM ATTN: SMUPA-VA6 Dover, New Jersey 07801	1	U. S. Naval Air Development Center ATTN: Technical Library Johnsville, Warminster, Pennsylvania 18974	1
U. S. Army Electronics Command ATTN: AMSEL-CB Fort Monmouth, New Jersey 07703	1	Frankford Arsenal ATTN: C-2500-Library Philadelphia, Pennsylvania 19137	1
Sandia Corporation ATTN: Technical Library P. O. Box 5800 Albuquerque, New Mexico 87115	1	Div. of Technical Information Ext., USAEC P. O. Box 62 Oak Ridge, Tennessee 37830	1
ORA(RRRT) Holloman Air Force Base, New Mexico 88330	1	Oak Ridge National Laboratory ATTN: Central Files P. O. Box X Oak Ridge, Tennessee 37830	1
Los Alamos Scientific Laboratory ATTN: Report Library P. O. Box 1663 Los Alamos, New Mexico 87544	1	Air Defense Agency, USACDC ATTN: Library Fort Bliss, Texas 79916	1
White Sands Missile Range ATTN: Technical Library White Sands, New Mexico 88002	1	U. S. Army Air Defense School ATTN: AKBAAS-DR-R Fort Bliss, Texas 79906	1
Rome Air Development Center (EMLAL-1) ATTN: Documents Library Griffiss Air Force Base, New York 13440	1		

	No. of Copies		No. of Copies
U. S. Army CDC Nuclear Group Fort Bliss, Texas 79916	1	<u>INTERNAL</u>	
Manned Spacecraft Center, NASA ATTN: Technical Library, Code BM6 Houston, Texas 77058	1	Headquarters U. S. Army Missile Command Redstone Arsenal, Alabama ATTN: AMSMI-D	1
Defense Documentation Center Cameron Station Alexandria, Virginia 22314	20	AMSMI-XE, Mr. Lowers	1
		AMSMI-XS, Dr. Carter	1
		AMSMI-Y	1
		AMSMI-R, Mr. McDaniel	1
		AMSMI-RAP	1
U. S. Army Research Office ATTN: STINFO Division 3045 Columbia Pike Arlington, Virginia 22204	1	AMSMI-RBLD	10
		USACDC-LnO	1
		AMSMI-RBT	8
		AMSMI-RB, Mr. Croxton	1
		AMSMI-RKC, Dr. Pittman	1
U. S. Naval Weapons Laboratory ATTN: Technical Library Dahlgren, Virginia 22448	1	National Aeronautics & Space Administration Marshall Space Flight Center Huntsville, Alabama	
U. S. Army Engineer Res. & Dev. Labs. ATTN: Scientific & Technical Info. Br. Fort Belvoir, Virginia 22060	2	ATTN: MS-T, Mr. Wiggins	5
Langley Research Center, NASA ATTN: Library, MS-185 Hampton, Virginia 23365	1		
Research Analysis Corporation ATTN: Library McLean, Virginia 22101	1		
U. S. Army Tank Automotive Center ATTN: SMOTA-RTS.1 Warren, Michigan 48090	1		
Hughes Aircraft Company Electronic Properties Information Center Florence Ave. & Teale St. Culver City, California 90230	1		
Atomics International, Div. of NAA Liquid Metals Information Center P. O. Box 309 Canoga Park, California 91305	1		
Foreign Technology Division ATTN: Library Wright-Patterson Air Force Base, Ohio 45400	1		
Clearinghouse for Federal Scientific and Technical Information U. S. Department of Commerce Springfield, Virginia 22151	1		
Foreign Science & Technology Center, USAMC ATTN: Mr. Shapiro Washington, D. C. 20315	3		

UNCLASSIFIED

Security Classification

DOCUMENT CONTROL DATA - R&D		
(Security classification of title, body of abstract and indexing annotation must be entered when the overall report is classified)		
1. ORIGINATING ACTIVITY (Corporate author) Redstone Scientific Information Center Research and Development Directorate U. S. Army Missile Command Redstone Arsenal, Alabama 35809		2a. REPORT SECURITY CLASSIFICATION Unclassified
		2b. GROUP N/A
3. REPORT TITLE EFFECT OF CERTAIN ADDITIVES ON THE THERMAL DECOMPOSITION OF AMMONIUM PERCHLORATE Izvestiya Vysshikh Uchebnykh Zavedeniy SSSR "Khimiya i Khimicheskaya Tekhnologiya" No. 4, 533-538 (1965)		
4. DESCRIPTIVE NOTES (Type of report and inclusive dates) Translated from the Russian		
5. AUTHOR(S) (Last name, first name, initial) Shidlovskiy, A. A., Shmagin, L. F., and Bulanova, V. V.		
6. REPORT DATE 25 January 1967	7a. TOTAL NO. OF PAGES 15	7b. NO. OF REFS 20
8a. CONTRACT OR GRANT NO. N/A	9a. ORIGINATOR'S REPORT NUMBER(S) RSIC-640	
b. PROJECT NO. N/A	9b. OTHER REPORT NO(S) (Any other numbers that may be assigned this report) AD	
c.		
d.		
10. AVAILABILITY/LIMITATION NOTICES Distribution of this document is unlimited.		
11. SUPPLEMENTARY NOTES None	12. SPONSORING MILITARY ACTIVITY Same as No. 1	
13. ABSTRACT 1) A study was made of the thermal decomposition of perchlorate of ammonium (PA) at 214° to 470°C by the gravimetric method in an air atmosphere. The following values of the energies of activation of the decomposition have been determined: orthorhombic form, E = 40 kcal/mole; cubic form, E = 24 to 28 kcal/mole; and residue from low-temperature reaction E = 36 to 39 kcal/mole. 2) A study was made of the influence of oxides, chlorides, carbonates, and oxalates of a number of metals on the thermal decomposition of PA. It was shown that the compounds of manganese and cobalt lead to complete decomposition of the PA at a temperature below 240°C. The compounds of iron, nickel, and chromium lead to complete decomposition of PA at 270° to 280°C. 3) At the same temperature, the maximum rate of decomposition of PA with additives of the compounds of Cu, Mn, Co, as well as ZnO is greater than the maximum decomposition rate of the pure PA; the maximum decomposition rate of mixtures of PA with compounds of iron, nickel (II), chromium, as well as V ₂ O ₅ is less than for pure PA. 4) The activity of additives of the same element decreases in the following order: carbonate (oxalate), oxide, and chloride.		

DD FORM 1 JAN 64 1473

UNCLASSIFIED

Security Classification

UNCLASSIFIED

Security Classification

14. KEY WORDS	LINK A		LINK B		LINK C	
	ROLE	WT	ROLE	WT	ROLE	WT
Thermal decomposition Gravimetric method Ammonium perchlorate Decomposition rate						

INSTRUCTIONS

1. ORIGINATING ACTIVITY: Enter the name and address of the contractor, subcontractor, grantee, Department of Defense activity or other organization (*corporate author*) issuing the report.

2a. REPORT SECURITY CLASSIFICATION: Enter the overall security classification of the report. Indicate whether "Restricted Data" is included. Marking is to be in accordance with appropriate security regulations.

2b. GROUP: Automatic downgrading is specified in DoD Directive 5200.10 and Armed Forces Industrial Manual. Enter the group number. Also, when applicable, show that optional markings have been used for Group 3 and Group 4 as authorized.

3. REPORT TITLE: Enter the complete report title in all capital letters. Titles in all cases should be unclassified. If a meaningful title cannot be selected without classification, show title classification in all capitals in parenthesis immediately following the title.

4. DESCRIPTIVE NOTES: If appropriate, enter the type of report, e.g., interim, progress, summary, annual, or final. Give the inclusive dates when a specific reporting period is covered.

5. AUTHOR(S): Enter the name(s) of author(s) as shown on or in the report. Enter last name, first name, middle initial. If military, show rank and branch of service. The name of the principal author is an absolute minimum requirement.

6. REPORT DATE: Enter the date of the report as day, month, year; or month, year. If more than one date appears on the report, use date of publication.

7a. TOTAL NUMBER OF PAGES: The total page count should follow normal pagination procedures, i.e., enter the number of pages containing information.

7b. NUMBER OF REFERENCES: Enter the total number of references cited in the report.

8a. CONTRACT OR GRANT NUMBER: If appropriate, enter the applicable number of the contract or grant under which the report was written.

8b, 8c, & 8d. PROJECT NUMBER: Enter the appropriate military department identification, such as project number, subproject number, system numbers, task number, etc.

9a. ORIGINATOR'S REPORT NUMBER(S): Enter the official report number by which the document will be identified and controlled by the originating activity. This number must be unique to this report.

9b. OTHER REPORT NUMBER(S): If the report has been assigned any other report numbers (*either by the originator or by the sponsor*), also enter this number(s).

10. AVAILABILITY/LIMITATION NOTICES: Enter any limitations on further dissemination of the report, other than those imposed by security classification, using standard statements such as:

- (1) "Qualified requesters may obtain copies of this report from DDC."
- (2) "Foreign announcement and dissemination of this report by DDC is not authorized."
- (3) "U. S. Government agencies may obtain copies of this report directly from DDC. Other qualified DDC users shall request through _____."
- (4) "U. S. military agencies may obtain copies of this report directly from DDC. Other qualified users shall request through _____."
- (5) "All distribution of this report is controlled. Qualified DDC users shall request through _____."

If the report has been furnished to the Office of Technical Services, Department of Commerce, for sale to the public, indicate this fact and enter the price, if known.

11. SUPPLEMENTARY NOTES: Use for additional explanatory notes.

12. SPONSORING MILITARY ACTIVITY: Enter the name of the departmental project office or laboratory sponsoring (*paying for*) the research and development. Include address.

13. ABSTRACT: Enter an abstract giving a brief and factual summary of the document indicative of the report, even though it may also appear elsewhere in the body of the technical report. If additional space is required, a continuation sheet shall be attached.

It is highly desirable that the abstract of classified reports be unclassified. Each paragraph of the abstract shall end with an indication of the military security classification of the information in the paragraph, represented as (TS), (S), (C), or (U).

There is no limitation on the length of the abstract. However, the suggested length is from 150 to 225 words.

14. KEY WORDS: Key words are technically meaningful terms or short phrases that characterize a report and may be used as index entries for cataloging the report. Key words must be selected so that no security classification is required. Identifiers, such as equipment model designation, trade name, military project code name, geographic location, may be used as key words but will be followed by an indication of technical context. The assignment of links, rules, and weights is optional.

UNCLASSIFIED

Security Classification